

**SINGLE CRYSTAL FILMS AND WAVEGUIDES OF ORGANIC MATERIALS;  
PREPARATION AND NONLINEAR OPTICAL PROPERTIES**

**(F49620-96-1-0063)**

**M. Thakur, Auburn University**

**Final Report**

The objectives of this program include: i) establishment of a method for the growth of thin single crystal films of important organic nonlinear optical materials, ii) detailed chemical and physical characterization of the films and iii) measurement of the nonlinear optical properties. We have successfully prepared single crystal thin films of several organic second order optical materials that include COANP, NPP, PNP, ABP, DAST and SPCD. These films were prepared using specific growth conditions following a method ("shear method"), invented by the principal investigator. This is the first time single crystal films of organic second order optical materials have been prepared. The areas of the films for COANP, NPP, PNP and ABP were large ( $>2 \text{ cm}^2$ ). For DAST the film-area was small  $\sim 20 \text{ mm}^2$ . The primary reason for the smaller area of DAST film was found to be its significantly lower solubility at ambient temperature and pressure.

The films of NPP, COANP, PNP and ABP have been characterized in detail by polarized optical microscopy, FTIR, optical absorption spectroscopy and x-ray diffraction. The studies have clearly elucidated the influence of polar interaction and predictability of molecular orientation in the shear-grown films. For example, both NPP and PNP molecules were found to organize along the substrate surface since the polar group was oriented sidewise with respect to the chromophore axis. In contrast, COANP molecules, having polar group along the molecular dipole axis, were oriented close to perpendicular to the substrate surface.

Detailed nonlinear optical measurements using second harmonic generation on the single crystal films have been completed for films of PNP and ABP. Measurements on NPP and COANP films were reported previously. The measurements have shown very large second order susceptibilities for the films. For example, the magnitude of  $d_{21}$  of NPP is  $97 \text{ pm/V}$  which is about 18 times that of the phase-matchable d-coefficient of  $\text{LiNbO}_3$ . The magnitude of  $d_{22}$  of COANP is  $56 \text{ pm/V}$ . These magnitudes are extremely large and the films can be used for autocorrelation measurements in diagnostics of ultrashort laser pulses. A measurement of the d-coefficients can provide a reasonable estimate of the electro-optic coefficients. The correlation between the d-

# REPORT DOCUMENTATION PAGE

The public reporting burden for this collection of information is estimated to average 1 hour per response, including gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments of information, including suggestions for reducing the burden, to Department of Defense, Washington Headquarters (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.


AFRL-SR-BL-TR-00-

81602

Des.  
tion  
orts  
ll be

1. REPORT DATE (DD-MM-YYYY) 10-04-2000		2. REPORT TYPE Final		3. DATES COVERED (From - To) April 1996 - March 1999	
4. TITLE AND SUBTITLE Single Crystal Films and Wave Guides of Organic Materials; Preparation and Nonlinear Optical Properties				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER F49620-96-1-0063	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S) Thakur, Mrinal				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Auburn University 310 Samford Hall Auburn University, AL 36849				8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) Air Force Office of Scientific Research 801 North Randolph St. Arlington, VA 22203 <i>NL</i>				10. SPONSOR/MONITOR'S ACRONYM(S) AFOSR	
				11. SPONSOR/MONITOR'S REPORT NUMBER(S)	
12. DISTRIBUTION/AVAILABILITY STATEMENT APPROVED FOR PUBLIC RELEASE: DISTRIBUTION UNLIMITED					
13. SUPPLEMENTARY NOTES					
14. ABSTRACT The objectives of this program include: i) establishment of a method for the growth of thin single crystal films of important organic nonlinear optical materials, ii) detailed chemical and physical characterization of the films and iii) measurement of the nonlinear optical properties. We have successfully accomplished these goals for several important organic materials. We have prepared and characterized single crystal films. The films of several materials have shown exceptionally large nonlinear optical and electro-optic coefficients. We expect a wide range of applications in photonics using such films.					
15. SUBJECT TERMS					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT  UU	18. NUMBER OF PAGES  6	19a. NAME OF RESPONSIBLE PERSON Mrinal Thakur
a. REPORT	b. ABSTRACT	c. THIS PAGE			19b. TELEPHONE NUMBER (Include area code) 334-844-3326

coefficient and electro-optic coefficient is:  $r_{ijk} = -4d_{ijk}/(n_{ii}n_{jj})^2$ . The d-tensor elements of the films were measured by second harmonic generation under various polarization conditions and with sample rotation. The results for a specific polarization condition, for a PNP sample (film orientation, [101]) is given in the following.


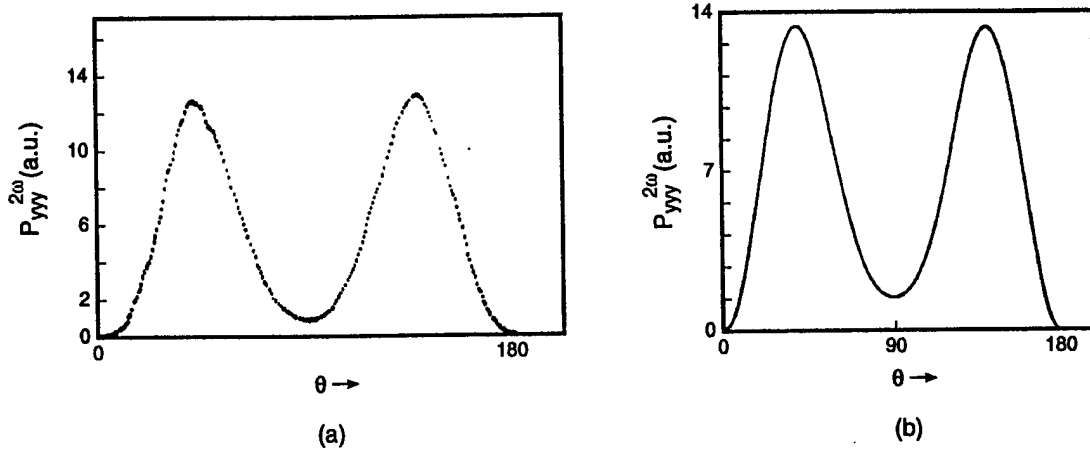


- a) Measured second harmonic power,  $P_{yyy}^{2\omega}$  for a PNP film as a function of angle of rotation of the film around the beam propagation direction. The input and output polarizations are parallel to each other.
- b) Calculated second harmonic power as a function of angle of rotation.

For PNP, the magnitude of  $d_{21}$  was  $65 (\pm 5)$  pm/V and the ratio  $d_{21}/d_{22}$  was equal to 2.5. This measurement technique has provided both sign and magnitudes of the second order tensor elements of the films.

We have recently reported electro-optic measurement on DAST films in the transverse configuration. A Ti:Sapphire laser was used for this measurement. The measurement was made using Mach-Zehnder interferometry and also by field-induced birefringence measurement in the cross-polarized configuration. Gold electrodes were deposited on the film to apply electric field in the transverse direction along the a-axis which lies on the film plane. The film with the electrodes was placed in one arm of the Mach-Zehnder interferometer to introduce phase changes using electric field while in the other arm light traveled through air. The laser light polarized parallel to the dipole axis (a-axis) was transmitted through the DAST film of thickness  $3\mu\text{m}$ . One of the corner mirrors of the Mach-Zehnder interferometer was attached to a piezoelectric drive to control the bias point in the Mach-Zehnder fringes. Light modulation at an optimum bias point was measured for different magnitudes of applied electric field using a photodiode and recorded using lock-in detection. At about 720 nm where absorption is small the measured phase change was extremely large and

therefore the intensity modulation was very large as detected using an oscilloscope. A modulation of 20% was observed for a field of  $1\text{V}/\mu\text{m}$  at  $4\text{kHz}$  (film thickness  $\sim 3\mu\text{m}$ ). The oscilloscope trace of the modulation signal for the field at  $4\text{kHz}$  is shown in the following. Clearly, the observed modulation is large for a thin film sample and this result provides the demonstration of a thin-film single-pass electro-optic modulator. The magnitude of  $r_{11}$  at  $720\text{nm}$  is  $530\text{pm}/\text{V}$ . Considering the reported d-coefficient of DAST ( $1900\text{pm}/\text{V}$  at  $1200\text{nm}$ ), such a high electro-optic coefficient can be expected. Speeds many orders of magnitude higher than  $4\text{kHz}$ , of-course, is expected and have been demonstrated for materials such as this. Therefore, the potential for applications of these films is significant. The geometry involving the field-induced birefringence is directly relevant to actual devices.

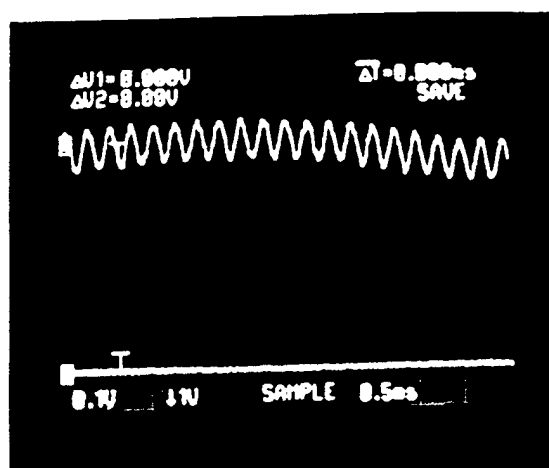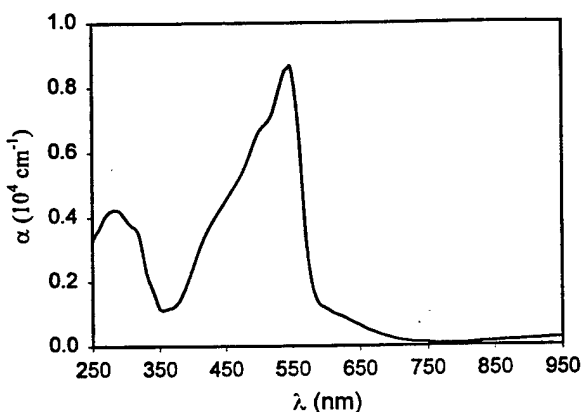


- a) The figure on the left gives the absorption spectrum of a DAST film.
- b) The figure on the right shows the oscilloscope trace for electro-optic modulation with about 20% modulation depth as measured for a thin-film of DAST. The measurement was made by field induced birefringence under cross-polarized condition at an optimum bias point. The applied field was  $1\text{V}/\mu\text{m}$  at  $4\text{kHz}$ .

Electro-optic modulation in a Fabry-Perot cavity containing a NPP film has been demonstrated. Channel waveguides were directly fabricated for NPP through growth on a patterned substrate. The guides thus obtained were characterized for electro-optic modulation and a large modulation was observed for a  $3\text{mm}$  long guide applying  $20\text{V d.c.}$

The off-resonant nonlinear refractive index has been measured for PTS-polydiacetylene crystal using z-scan and Michelson interferometry. The sign was unequivocally negative and the magnitude was ( $10^{-5}\text{ cm}^2/\text{MW}$ ) consistent with previous reports. This result clearly shows that

bleaching of the exciton absorption has the dominant contribution to the optical nonlinearity of PTS-polydiacetylene. Significant spectral broadening due to self-phase modulation (off-resonant nonlinear refractive index) was observed in a PTS-polydiacetylene crystal using 2ps pulses at low intensities. This result shows promise for using this material for pulse compression application. Picosecond all-optical switching with 50% modulation depth was previously demonstrated in the Fabry-Perot geometry at 1.06 $\mu$ m.

We have observed strong polarization dependent photoluminescence in both phases of DAST single crystal films for excitation at 400nm with 2ps pulses from a Ti:Sapphire laser. The photoluminescence peaks appeared at 610nm for the red phase (noncentrosymmetric) and at 585nm for the orange phase (centrosymmetric). These results are promising for potential applications of the films in LEDs and lasers.

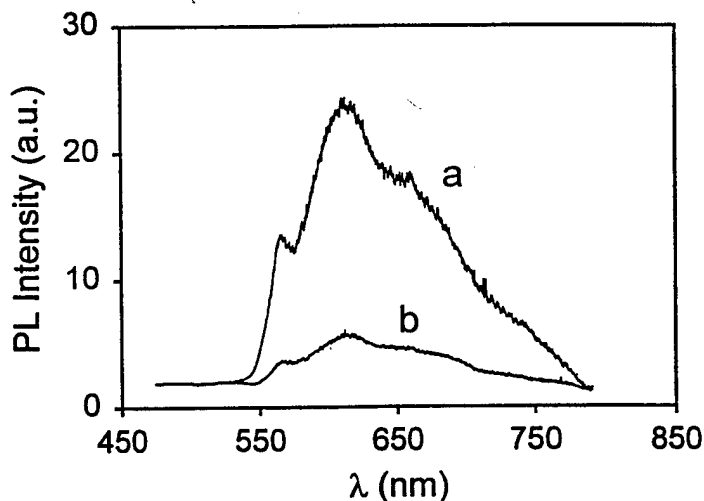

The photoluminescence spectra of DAST (red phase) for: a) incident polarization parallel to the dipole axis and b) incident polarization perpendicular to the dipole axis.

Thus, as these results show, we have made significant progress in both growth of single crystal films as well as nonlinear optical measurements of several important organic materials. In the future, we intend to make substantial improvement in the thin-film crystal growth of some of the key organic materials such as the stilbazolium salts and specific other materials and make detailed nonlinear optical measurements on the single crystal films over a wide range of wavelengths. We will also fabricate specific device structures using these films.

## **Publications:**

1. "Single-pass Thin-film Electro-optic Modulator based on an Organic Molecular Salt", M. Thakur, J. Xu, A. Bhowmik and L. Zhou, Appl. Phys. Lett., 74 635 (1999).
2. "Second Harmonic Generation in Single Crystal Films of 4-Aminobenzophenone (ABP)", A. Bhowmik, J. Wang and M. Thakur, J. Appl. Phys. 86 923 (1999).
3. "Polarized optical absorption and photoluminescence measurements in single-crystal thin films of 4'-dimethylamino-N-methyl-4-stilbazolium tosylate", A. Bhowmik, J. Xu and M. Thakur, Appl. Phys. Lett., 75 3291 (1999).
4. "Second Harmonic Generation in Single Crystal Films of an Organic Material (COANP)", R. Quintero-Torres and M. Thakur, Opt. Lett., 19 87 (1994); R. Quintero-Torres, Jianjun Xu and M. Thakur, Polym. Prepr., 35 No. 2 189 (1994).
5. "Molecular Organization in Single Crystal Thin Films of N-(4-nitrophenyl)-(L)-prolinol (NPP)", L. Zhou and M. Thakur, J. Mater Res., 13 131 (1998).
6. "Nonlinear Optical Studies of Single Crystal Films of N-(4-nitrophenyl)-(L)-prolinol", R. Quintero-Torres and M. Thakur, Appl. Phys. Lett., 69 1994 (1996).
7. "Second Harmonic Generation in Single-Thin Films of 2-(N-prolinol)-5-nitropyridine (PNP)", L. Zhou and M. Thakur, Opt. Eng., 36 1262 (1997).
8. "Measurement of Electro-optic Effects in Single Crystal Films of N-(4-nitrophenyl)-L-prolinol", Jianjun Xu, L. Zhou and M. Thakur, Appl. Phys. Lett., 69 1197 (1996).
9. "Electro-optic Modulation using an Organic Single Crystal Film in a Fabry-Perot Cavity", J. Xu, L. Zhou and M. Thakur, Appl. Phys. Lett., 72 153 (1997).
10. "SPM-induced Spectral Broadening in PTS-polydiacetylene crystal", A. Bhowmik and M. Thakur, APS March meeting, Los Angeles, CA, March, 1998.
11. "Growth of Single Crystal Channel Waveguides of NPP", Jianjun Xu and M. Thakur, ACS Meeting, Long Island, CA, October, 1997.

12. "Measurement of Nonlinear Refractive Index of PTS-polydiacetylene by Z-scan and Michelson Interferometry", R. Quintero-Torres and M. Thakur, J. Appl. Phys., 85 401 (1999).
13. "Picosecond All-optical Switching in a Fabry-Perot Cavity Containing Polydiacetylene", R. Quintero-Torres and M. Thakur, Appl. Phys. Lett., 66 1310 (1995).

**Students Supported:**

This project has partially supported three Ph.D. students: Jianjun Xu, Ligui Zhou and Achintya Bhowmik. Jianjun and Ligui have graduated and are presently employed in industrial R&D. Achintya is continuing his graduate studies.